


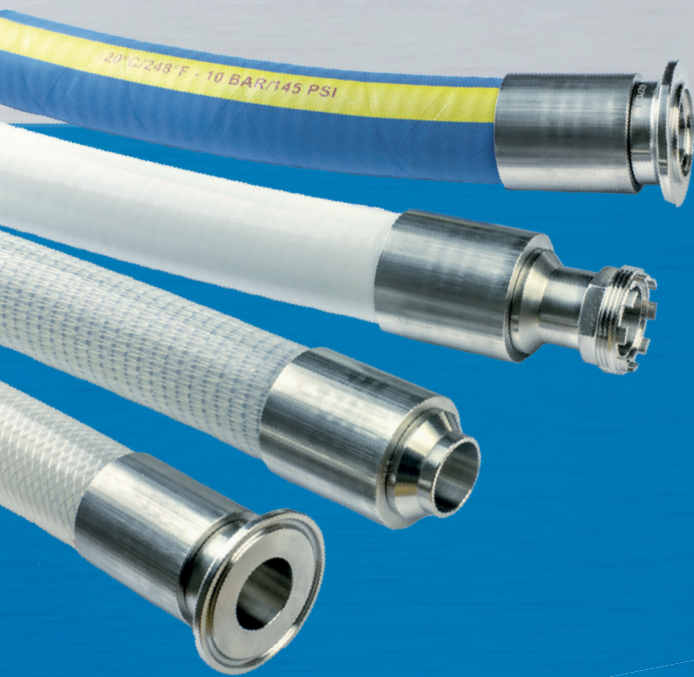

# RESISTANCE LIST

# BESTÄNDIGKEITSLISTE

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                            | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|--------------------------------------|------|----------------|-----------|
| A                                    |      |                |           |
| ACETALDEHYDE                         | A    | A              | A         |
| ACETAMIDE                            | A    | B              | A         |
| ACETATE SOLVENT                      | A    | C              | A         |
| ACETIC ACID                          | A    | C              | A         |
| ACETIC ACID 05%                      | A    | A              |           |
| ACETIC ACID 20%                      | A    | B              | A         |
| ACETIC ACID 30%                      | A    | A              |           |
| ACETIC ACID 80%                      | A    | B              | A         |
| ACETIC ACID, GLACIAL                 | B    | B              | A         |
| ACETIC ACID, HOT HIGH PRESSURE       | C    | C              |           |
| ACETIC ANHYDRIDE                     | B    | C              | A         |
| ACETONE                              | A    | B              | A         |
| ACETOPHENONE                         | A    | D              |           |
| ACETYL ACETONE                       | A    | D              |           |
| ACETYL CHLORIDE ( DRY )              | D    | C              | A         |
| ACETYLENE                            | A    | B              | A         |
| ACETYLENE TETRABOMIDE                | A    |                |           |
| ACRYLONITRILE                        | D    | D              | A         |
| ADIPIC ACID                          |      |                |           |
| AERO LUBRIPLATE                      | D    | B              |           |
| AERO SAFE 2300                       | A    | C              |           |
| AERO SHELL 17 GREASE                 | D    | B              |           |
| AERO SHELL 7 A GREASE                | D    | B              |           |
| AERO SHELL 750                       | D    | D              |           |
| AERO SHELL IAC                       | D    | B              |           |
| AEROZENE 50 (50% HYDRAZINE 50% UDMH) | A    | D              |           |
| AIR ABOVE 300°F                      | D    | A              |           |
| AIR BELOW 300°F                      | B    | A              |           |
| ALCOHOLS :AMYL                       | A    | D              | A         |
| ALCOHOLS :BENZYL                     | B    |                | A         |
| ALCOHOLS :BUTYL                      | B    | B              | A         |
| ALCOHOLS :DIACETONE                  | A    | D              | A         |
| ALCOHOLS :ETHYL                      | A    | B              | A         |
| ALCOHOLS :HEXYL                      | C    | B              | A         |
| ALCOHOLS :ISOBUTYL                   | A    | A              | A2        |
| ALCOHOLS :ISOPROPYL                  | A    | A              | A2        |
| ALCOHOLS :METHYL                     | A    | A              | A         |
| ALCOHOLS :METHYL ALCOHOL 10%         | A    | A              | A         |
| ALCOHOLS :OCTYL                      | A    | B              |           |
| ALCOHOLS :PROPYL                     | A    | A              | A         |
| ALKAZENE                             | D    | D              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                            | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|--------------------------------------|------|----------------|-----------|
| A                                    |      |                |           |
| ALUM NH3 CR-K                        | A    | A              |           |
| ALUMINUM ACETATE                     | A    | D              |           |
| ALUMINUM BROMIDE                     | A    | A              |           |
| ALUMINUM CHLORIDE 20%                | A    | B              | A         |
| ALUMINUM FLUORIDE                    | A    | B              | A         |
| ALUMINUM HYDROXIDE                   | A    |                | A         |
| ALUMINUM NITRATE                     | A    | B              |           |
| ALUMINUM PHOSPHATE                   | A    | A              |           |
| ALUMINUM POTASSIUM SULFATE 10%       | A    | A              | A         |
| ALUMINUM POTASSIUM SULFATE 100%      | A    | A              | A         |
| ALUMINUM SALTS                       | A    | A              |           |
| ALUMINUM SULFATE                     | A    | A              | A         |
| AMBREX 33 MOBIL                      | D    | D              |           |
| AMINES                               | B    | B              | A2        |
| AMMONIA 10%                          | A    |                | A         |
| AMMONIA AND LITHIUM METALIN SOLUTION | B    | D              |           |
| AMMONIA ANHYDROUS (LIQUID)           | A    | C              |           |
| AMMONIA GAS, COLD                    | A    | A              |           |
| AMMONIA GAS, HOT                     | B    | A              |           |
| AMMONIA NITRATE                      | A    |                | A         |
| AMMONIA, ANHYDROUS                   | A    | D              | A         |
| AMMONIA, LIQUID                      | A    |                | A         |
| AMMONIUM BIFLUORIDE                  | A2   |                | A         |
| AMMONIUM CARBONATE                   | A    |                | A         |
| AMMONIUM CASENITE                    |      |                |           |
| AMMONIUM CHLORIDE                    | A    | A              | A         |
| AMMONIUM HYDROXIDE (CONCENTRATED)    | A    | A              | A         |
| AMMONIUM NITRATE                     | A    |                |           |
| AMMONIUM NITRITE                     | A    | B              |           |
| AMMONIUM OXALATE                     |      |                |           |
| AMMONIUM PERSULFATE                  | A    | A              | A1        |
| AMMONIUM PERSULFATE 10%              | A    |                |           |
| AMMONIUM PERSULFATE SOLUTION         | A    |                |           |
| AMMONIUM PHOSPHATE                   | A    | A              |           |
| AMMONIUM PHOSPHATE, DIBASIC          | A    | A              | A2        |
| AMMONIUM PHOSPHATE, MONOBASIC        | A    | A              | A         |
| AMMONIUM PHOSPHATE, TRIBASIC         | A    | A              | A         |
| AMMONIUM SALTS                       | A    | A              |           |
| AMMONIUM SULFATE                     | A    | A              | A         |
| AMMONIUM SULFIDE                     | A    |                |           |
| AMMONIUM THIOSULFATE                 |      | D              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                        | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|----------------------------------|------|----------------|-----------|
| A                                |      |                |           |
| AMMONUIM NITRATE                 | A    |                | A         |
| AMYL ACETATE                     | A    | D              |           |
| AMYL BORATE                      | D    |                |           |
| AMYL CHLORANAPHTHALENE           | D    | D              |           |
| AMYL CHORIDE                     | D    | D              | A         |
| AMYL NAPHTHALENE                 | D    | D              |           |
| AN-0-3 GRADE M                   | D    | B              |           |
| AN-0-366                         | D    | D              |           |
| AN-0-6                           | D    | D              |           |
| ANDEROL L774 (DI-ESTER)          | D    | D              |           |
| ANDEROL L-826 (DI-ESTER)         | D    | D              |           |
| ANDEROL L-829 (DI-ESTER)         | D    | D              |           |
| ANG-25 (DI-ESTER BASE) (TG749)   | D    | B              |           |
| ANG-25 (GLYCERAL ESTER)          | A    | B              |           |
| ANHYDROUS AMMONIA                | A    | B              |           |
| ANHYDROUS HYDRAZINE              | B    |                |           |
| ANHYDROUS HYDROGEN FLUORIDE      | A    |                |           |
| ANILINE                          | B    | D              | A         |
| ANILINE DYES                     | B    | C              |           |
| ANILINE HYDROCHLORIDE            | C    | D              |           |
| ANILINE OILS                     | B    | D              |           |
| ANIMAL FATS                      | B    | B              |           |
| ANIMAL OILS (LARD OIL)           | B    | B              |           |
| ANSUL ETHER                      | C    | D              |           |
| ANTI-FREEZE                      |      |                |           |
| ANTIMONY TRICHLORIDE             | B1   |                | A         |
| AN-V V-O-366 B HYDR. FLUID       | D    | D              |           |
| AQUA REGIA ( 80% HCl, 20% HNO3 ) | C    | D              | A         |
| ARGON                            | A    | B              |           |
| AROCHLOR 1248                    | B    | B              | A         |
| AROCHLOR 1254                    | B    | C              |           |
| AROCHLOR 1260                    |      | A              |           |
| AROMATIC FUEL 50%                | D    | D              |           |
| AROMATIC HYDROCARBONS            | D    | D              |           |
| ARSENIC ACID                     | A2   | A              | A         |
| ARSENIC TRICHLORIDE              |      |                |           |
| ASKAREL                          | D    | D              |           |
| ASPHALT                          | D    | D              | A1        |
| ASTM OIL #1                      | D    | A              |           |
| ASTM OIL #2                      | D    | D              |           |
| ASTM OIL #3                      | D    | C              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                    | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|------------------------------|------|----------------|-----------|
| A                            |      |                |           |
| ASTM OIL #4                  | D    | D              |           |
| ASTM REFERENCE FUEL A        | D    | D              |           |
| ASTM REFERENCE FUEL B        | D    | D              |           |
| ASTM REFERENCE FUEL C        | D    | D              |           |
| ATL-857                      | D    | D              |           |
| ATLANTIC DOMINION F          | D    | D              |           |
| AUREX 903R MOBIL             | D    | D              |           |
| AUTOMATIC TRANSMISSION FLUID | D    | D              |           |
| AUTOMOTIVE BRAKE FLUID       | A    | C              |           |
| B                            |      |                |           |
| BARDOL B                     | D    | D              |           |
| BARIUM CARBONATE             | A    |                | A         |
| BARIUM CHLORIDE              | A    | A              | A         |
| BARIUM CYANIDE               | A    |                | A1        |
| BARIUM HYDROXIDE             | A    | A              | A         |
| BARIUM NITRATE               | A    |                | A1        |
| BARIUM SALTS                 | A    | A              |           |
| BARIUM SULFATE               | A    | A              | A         |
| BARIUM SULFIDE               | A    | A              | A         |
| BAYOL D                      | D    | D              |           |
| BEER                         | A    | A              | A         |
| BEET SUGAR LIQUID            | A    | A              | A1        |
| BENZALDEHYDE                 | A    | D              | A1        |
| BENZENE                      | D    | D              | A         |
| BENZENESULFONIC ACID         | D    | D              |           |
| BENZINE                      | D    | D              |           |
| BENZOCHLORIDE                | A    |                |           |
| BENZOIC ACID                 | D    | B              | A2        |
| BENZOL                       | B    |                | A         |
| BENZOPHENONE                 | B    |                |           |
| BENZYL BENZOATE              | B    |                |           |
| BENZYL CHLORIDE              | D    | D              |           |
| BLACK POINT 77               | A    | C              |           |
| BLACK SULPHATE LIQUORS       | B    | B              |           |
| BLAST FURNACE GAS            | D    | A              |           |
| BLEACH SOLUTIONS             | A    | B              |           |
| BORAX ( SODIUM BORATE )      | A    | B              | A         |
| BORDEAUX MIXTURE             | A    | B              |           |
| BORIC ACID                   | A    | A              |           |
| BORON FLUIDS (HEF)           | D    | D              |           |
| BRAKE FLUID (NON PETROLEUM)  | A    | C              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                        | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|----------------------------------|------|----------------|-----------|
| A                                |      |                |           |
| AMMONUIM NITRATE                 | A    |                | A         |
| AMYL ACETATE                     | A    | D              |           |
| AMYL BORATE                      | D    |                |           |
| AMYL CHLORANAPHTHALENE           | D    | D              |           |
| AMYL CHORIDE                     | D    | D              | A         |
| AMYL NAPHTHALENE                 | D    | D              |           |
| AN-0-3 GRADE M                   | D    | B              |           |
| AN-0-366                         | D    | D              |           |
| AN-0-6                           | D    | D              |           |
| ANDEROL L774 (DI-ESTER)          | D    | D              |           |
| ANDEROL L-826 (DI-ESTER)         | D    | D              |           |
| ANDEROL L-829 (DI-ESTER)         | D    | D              |           |
| ANG-25 (DI-ESTER BASE) (TG749)   | D    | B              |           |
| ANG-25 (GLYCERAL ESTER)          | A    | B              |           |
| ANHYDROUS AMMONIA                | A    | B              |           |
| ANHYDROUS HYDRAZINE              | B    |                |           |
| ANHYDROUS HYDROGEN FLUORIDE      | A    |                |           |
| ANILINE                          | B    | D              | A         |
| ANILINE DYES                     | B    | C              |           |
| ANILINE HYDROCHLORIDE            | C    | D              |           |
| ANILINE OILS                     | B    | D              |           |
| ANIMAL FATS                      | B    | B              |           |
| ANIMAL OILS (LARD OIL)           | B    | B              |           |
| ANSUL ETHER                      | C    | D              |           |
| ANTI-FREEZE                      |      |                |           |
| ANTIMONY TRICHLORIDE             | B1   |                | A         |
| AN-V V-O-366 B HYDR. FLUID       | D    | D              |           |
| AQUA REGIA ( 80% HCl, 20% HNO3 ) | C    | D              | A         |
| ARGON                            | A    | B              |           |
| AROCHLOR 1248                    | B    | B              | A         |
| AROCHLOR 1254                    | B    | C              |           |
| AROCHLOR 1260                    |      | A              |           |
| AROMATIC FUEL 50%                | D    | D              |           |
| AROMATIC HYDROCARBONS            | D    | D              |           |
| ARSENIC ACID                     | A2   | A              | A         |
| ARSENIC TRICHLORIDE              |      |                |           |
| ASKAREL                          | D    | D              |           |
| ASPHALT                          | D    | D              | A1        |
| ASTM OIL #1                      | D    | A              |           |
| ASTM OIL #2                      | D    | D              |           |
| ASTM OIL #3                      | D    | C              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                    | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|------------------------------|------|----------------|-----------|
| A                            |      |                |           |
| ASTM OIL #4                  | D    | D              |           |
| ASTM REFERENCE FUEL A        | D    | D              |           |
| ASTM REFERENCE FUEL B        | D    | D              |           |
| ASTM REFERENCE FUEL C        | D    | D              |           |
| ATL-857                      | D    | D              |           |
| ATLANTIC DOMINION F          | D    | D              |           |
| AUREX 903R MOBIL             | D    | D              |           |
| AUTOMATIC TRANSMISSION FLUID | D    | D              |           |
| AUTOMOTIVE BRAKE FLUID       | A    | C              |           |
| B                            |      |                |           |
| BARDOL B                     | D    | D              |           |
| BARIUM CARBONATE             | A    |                | A         |
| BARIUM CHLORIDE              | A    | A              | A         |
| BARIUM CYANIDE               | A    |                | A1        |
| BARIUM HYDROXIDE             | A    | A              | A         |
| BARIUM NITRATE               | A    |                | A1        |
| BARIUM SALTS                 | A    | A              |           |
| BARIUM SULFATE               | A    | A              | A         |
| BARIUM SULFIDE               | A    | A              | A         |
| BAYOL D                      | D    | D              |           |
| BEER                         | A    | A              | A         |
| BEET SUGAR LIQUID            | A    | A              | A1        |
| BENZALDEHYDE                 | A    | D              | A1        |
| BENZENE                      | D    | D              | A         |
| BENZENESULFONIC ACID         | D    | D              |           |
| BENZINE                      | D    | D              |           |
| BENZOCHLORIDE                | A    |                |           |
| BENZOIC ACID                 | D    | B              | A2        |
| BENZOL                       | B    |                | A         |
| BENZOPHENONE                 | B    |                |           |
| BENZYL BENZOATE              | B    |                |           |
| BENZYL CHLORIDE              | D    | D              |           |
| BLACK POINT 77               | A    | C              |           |
| BLACK SULPHATE LIQUORS       | B    | B              |           |
| BLAST FURNACE GAS            | D    | A              |           |
| BLEACH SOLUTIONS             | A    | B              |           |
| BORAX ( SODIUM BORATE )      | A    | B              | A         |
| BORDEAUX MIXTURE             | A    | B              |           |
| BORIC ACID                   | A    | A              |           |
| BORON FLUIDS (HEF)           | D    | D              |           |
| BRAKE FLUID (NON PETROLEUM)  | A    | C              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                   | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-----------------------------|------|----------------|-----------|
| B                           |      |                |           |
| BRAY GG-130                 | D    | D              |           |
| BRAYCO 719-R (VV-H-910)     | A    | B              |           |
| BRAYCO 885 (MIL-L-6085A)    | D    | D              |           |
| BRAYCO 910                  | A    | D              |           |
| BRET 710                    | A    | D              |           |
| BREWERY SLOP                |      |                |           |
| BRINE                       | A    |                |           |
| BROM-113                    | D    | D              |           |
| BROM-114                    | D    | D              |           |
| BROMINE                     | D    | D              | A         |
| BROMINE ANHYDROUS           |      | C              |           |
| BROMINE PENTAFLUORIDE       | D    | D              |           |
| BROMINE TRIFLUORIDE         | D    | D              |           |
| BROMINE WATER               | D    | D              |           |
| BROMOBENZENE                | D    | D              |           |
| BROMOCHLORO TRIFLUOROETHANE | D    | D              |           |
| BUNKER OIL                  | D    | B              |           |
| BUTADIENE                   | C    | D              | A2        |
| BUTANE                      | D    | D              | A         |
| BUTANE 2,2 - DIMETHYL       | D    | D              |           |
| BUTANE 2,3 - DIMETHYL       | D    | D              |           |
| BUTANOL ( BUTYL ALCOHOL )   | B    | B              | A2        |
| BUTENE/2-ETHYL              | D    | D              |           |
| BUTHYL ACETATE              | B    | D              |           |
| BUTTER                      | A    | B              | A         |
| BUTTERMILK                  |      |                | A         |
| BUTYL ACETYL RICINOLEATE    | A    |                |           |
| BUTYL ACRYLATE              | D    |                |           |
| BUTYL AMINE                 | D    | B              |           |
| BUTYL BENZOATE              | A    |                |           |
| BUTYL BUTYRATE              | A    |                |           |
| BUTYL CARBITOL              | A    | D              |           |
| BUTYL CELLOSOLVE            | A    |                |           |
| BUTYL CELLOSOLVE ADIPATE    | B    | B              |           |
| BUTYL ETHER                 | C    | D              |           |
| BUTYL OLEATE                | B    |                |           |
| BUTYL STEARATE              | B    |                |           |
| BUTYLACETATE                | B    | D              | A         |
| BUTYLENE                    | D    | D              | A         |
| BUTYRALDEHYDE               | B    | D              |           |
| BUTYRIC ACID                | B    |                | A2        |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                    | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|------------------------------|------|----------------|-----------|
| C                            |      |                |           |
| CALCINE LIQUORS              | A    |                |           |
| CALCIUM ACETATE              | A    | D              |           |
| CALCIUM BISULFATE            |      |                |           |
| CALCIUM BISULFIDE            | C    |                | A         |
| CALCIUM BISULFITE            | D    | A              | A         |
| CALCIUM CARBONATE            | A    | A              | A         |
| CALCIUM CHLORATE             | A    |                | A         |
| CALCIUM CHLORIDE             | A    | A              | A         |
| CALCIUM CYANIDE              | A    | A              |           |
| CALCIUM HYDROXIDE            | A    | A              | A         |
| CALCIUM HYPOCHLORITE         | B1   | B              | A         |
| CALCIUM HYPOCHLORIDE         | A    |                |           |
| CALCIUM NITRATE              | A    | B              |           |
| CALCIUM PHOSPHATE            | A    | A              |           |
| CALCIUM SALTS                | A    | B              |           |
| CALCIUM SILICATE             | A    |                |           |
| CALCIUM SULFATE              | A    |                | A         |
| CALCIUM SULFIDE              | A    | B              |           |
| CALCIUM SULFITE              | A    | A              |           |
| CALCIUM THIOSULFATE          | A    | A              |           |
| CALGON                       | A    |                |           |
| CALICHE LIQUORS              | A    | B              |           |
| CANE JUICE                   | A    | A              | A         |
| CANE SUGAR LIQUORS           | A    | A              |           |
| CAPROIC ALDEHYDE             | B    | B              |           |
| CARBAMATE                    | B    |                |           |
| CARBITOL                     | B    | B              |           |
| CARBOLIC ACID                | B    | D              |           |
| CARBOLIC ACID ( SEE PHENOL ) | B    | D              | A         |
| CARBON BISULFIDE             | D    |                |           |
| CARBON DIOXIDE               | B    | B              | A         |
| CARBON DIOXIDE ( WET )       | B    | B              | A         |
| CARBON DIOXIDE (DRY)         | B    | B              |           |
| CARBON DISULFIDE             | D    |                | A         |
| CARBON MONOXIDE              | A    | A              | A         |
| CARBON TETRACHLORIDE         | D    | D              | A         |
| CARBONATED WATER             |      |                |           |
| CARBONIC ACID                | A    | A              | A         |
| CASTOR OIL                   | B    | A              |           |
| CATSUP                       | C    |                |           |
| CELLOSOLVE                   | B    | D              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                      | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|------------------------------------------------|------|----------------|-----------|
| C                                              |      |                |           |
| CELLOSOLVE ACETATE                             | B    | D              |           |
| CELLOSOLVE BUTYL                               | B    | D              |           |
| CELLUGUARD                                     | A    | A              |           |
| CELLULUBE 90,100,150,220,300,500               | A    | A              |           |
| CELLULUBE A60 (NOW FYRQUEL)                    | A    |                |           |
| CELLUTHERM 2505A                               | D    | D              |           |
| CETATE (HEXADECANE)                            | D    | D              |           |
| CHINA WOOD OIL (TUNG OIL)                      | D    | D              |           |
| CHLORACETIC ACID                               | B    |                |           |
| CHLOREXTOL                                     | D    | D              |           |
| CHLORIC ACID                                   |      |                | A         |
| CHLORINATED CLUE                               | B    |                |           |
| CHLORINATED SALT BRINE                         | D    | D              |           |
| CHLORINATED SOLVENTS, DRY                      | D    | D              |           |
| CHLORINATED SOLVENTS, WET                      | D    | D              |           |
| CHLORINE (WET)                                 | C    |                |           |
| CHLORINE DIOXIDE                               | C    |                |           |
| CHLORINE DIOXIDE (8% CI AS NACIO2 IN SOLUTION) | D    |                |           |
| CHLORINE TRIFLUORIDE                           | D    | D              |           |
| CHLORINE WATER                                 | C    |                | A         |
| CHLORINE, ANHYDROUS LIQUID                     | C    |                | A         |
| CHLORINE, DRY                                  | A    | D              | A         |
| CHLORO/1-NITRO ETHANE                          | D    | D              |           |
| CHLOROACETIC ACID                              | B    |                | A         |
| CHLOROACETONE                                  | A    | D              |           |
| CHLOROBENZENE                                  | D    | D              |           |
| CHLOROBENZENE ( MONO )                         | D    | D              | B         |
| CHLOROBROMO METHANE                            | B    | D              |           |
| CHLOROBUTADIENE                                | D    | D              |           |
| CHLORODANE                                     | D    | D              |           |
| CHLORODODECANE                                 | D    | D              |           |
| CHLOROFORM                                     | D    | D              | A1        |
| CHLORONAPHTANENE                               | D    | D              |           |
| CHLOROSULFONIC ACID                            | D    | D              | A         |
| CHLOROTOLUENE                                  | D    | D              |           |
| CHLOROX                                        | B    |                |           |
| CHLORPHENOL                                    | D    | D              |           |
| CHOCOLATE SYRUP                                |      |                | A         |
| CHROME ALUM                                    | A    | A              |           |
| CHROME PLATING SOLUTION                        | D    | B              |           |
| CHROMIC ACID 05%                               | A    | C              | A         |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                        | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|--------------------------------------------------|------|----------------|-----------|
| C                                                |      |                |           |
| CHROMIC ACID 10%                                 | C    | C              | A         |
| CHROMIC ACID 30%                                 | B    | C              | A         |
| CHROMIC ACID 50%                                 | B    | C              | A2        |
| CHROMIC OXIDE 88 WT, % AQUEOUS SOLUTION          | B    | B              |           |
| CIDER                                            |      |                |           |
| CIRCO LIGHT PROCESS OIL                          | D    | D              |           |
| CITRIC ACID                                      | A    | A              | A         |
| CITRIC OILS                                      |      |                |           |
| CITY SERVICE #65, #120, #250                     | D    | D              |           |
| CITY SERVICE KOOLMOTOR-AP GEAR OIL 140-E,P, LUBE | D    | D              |           |
| CITY SERVICE PACEMAKER #2                        | D    | D              |           |
| COBALT CHLORIDE                                  | A    | B              |           |
| COBALT CHLORIDE, 2N                              | A    | A              |           |
| COCOANUT OIL                                     | C    | A              |           |
| COD LIVER OIL                                    | A    | B              |           |
| COFFEE                                           | A    | A              |           |
| COKE OVEN GAS                                    | D    | B              |           |
| COLICHE LIQUORS                                  | B    |                |           |
| CONVELEX 10                                      |      | D              |           |
| COOLANOL (MONSANTO)                              | D    | D              |           |
| COOLANOL 45 (MONSANTO)+A269                      | D    | D              |           |
| COPPER ACETATE                                   | A    | D              |           |
| COPPER CHLORIDE                                  | A    | A              | A         |
| COPPER CYANIDE                                   | A    | A              | A         |
| COPPER FLUOBORATE                                |      |                |           |
| COPPER NITRATE                                   |      |                | A         |
| COPPER SALTS                                     | A    | A              |           |
| COPPER SULFATE > 5%                              | A    | A              | A         |
| COPPER SULFATE 5%                                | A    | A              | A         |
| COPPER SULFATE 50%                               | A    | A              |           |
| CORN OIL                                         | C    | A              |           |
| COTTONSEED OIL                                   | C    | A              |           |
| CREAM                                            |      |                | A         |
| CREOSOLS                                         | D    | D              |           |
| CREOSOTE                                         | D    | D              |           |
| CREOSOTE, COAL TAR                               | D    | D              |           |
| CREOSOTE, WOOD                                   | D    | D              |           |
| CREOSYLIC ACID                                   | D    | D              |           |
| CRESOLS                                          | D    | D              |           |
| CRISYLIC ACID                                    | D    | D              | A         |
| CRUDE OIL                                        | D    | D              |           |

RESISTANCE LIST DOCKWEILER HOSES  
BESTÄNDIGKEITSLISTE FÜR DAS DOCKWEILER SCHLAUCHPROGRAMM

- Chemicals / Chemikalien**  
**A** - No effect / Keine Auswirkung  
**B** - Minor Effect-Good / Geringe Auswirkung  
**C** - Moderate Effect-Fair / Mäßige Auswirkung  
**D** - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
**1** - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
**2** - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                     | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-------------------------------|------|----------------|-----------|
| C                             |      |                |           |
| CUMENE                        | D    | D              |           |
| CUTTING OIL                   | D    | D              |           |
| CYANIC ACID                   |      |                | A         |
| CYCLOHEXANE                   | D    | D              | A         |
| CYCLOHEXANOL                  | D    | D              |           |
| CYCLOHEXANONE                 | B    | D              |           |
| D                             |      |                |           |
| DECALIN                       | D    | D              |           |
| DECANE                        | D    | B              |           |
| DELCO BRAKE FLUID             | A    | C              |           |
| DENATURED ALCOHOL             | A    | A              |           |
| DETERGENTS                    | A    | A              | A         |
| DEVELOPING FLUIDS (PHOTO)     | B    | A              |           |
| DEXTRON                       | D    | D              |           |
| DIAZINON                      | D    | D              |           |
| DIBENZYL ETHER                | B    |                |           |
| DIBENZYL SEBACATE             | B    | C              |           |
| DIBROMOETHYL BENZENE          | D    | D              |           |
| DIBUTY SEBACATE               | B    | B              |           |
| DIBUTYL ETHER                 | C    | D              |           |
| DIBUTYL PHTHALATE             | A    | B              |           |
| DIBUTYLAMINE                  | D    | C              |           |
| DICHLORETHAN                  |      |                | A1        |
| DICHLORO-BUTANE               | D    | D              |           |
| DICHLORO-ISOPROPYL ETHER      | C    | D              |           |
| DICYCLOHEXYLAMINE             | D    |                |           |
| DIESEL FUEL                   | D    | D              | A         |
| DI-ESTER LUBRICANT MIL-L-7808 | D    | D              |           |
| DI-ESTER SYNTHETIC LUBRICANTS | D    | D              |           |
| DIETHYL BENEZENE              | D    | D              |           |
| DIETHYL ETHER                 | D    | D              |           |
| DIETHYL SEBACATE              | B    | B              |           |
| DIETHYLAMINE                  | B    | B              | A         |
| DIETHYLENE GLYCOL             | A    | B              | A2        |
| DIFLUORODIBROMOMETHANE        | B    | D              |           |
| DIISOBUTYLENE                 | D    | D              |           |
| DIISOCTYL SEBACATE            | C    | C              |           |
| DIISOPROPYL BENZENE           | D    |                |           |
| DIISOPROPYL KETONE            | A    | D              |           |
| DIMETHYL ANILINE              | B    |                |           |
| DIMETHYL FORMAMIDE            | B    | B              |           |

RESISTANCE LIST DOCKWEILER HOSES  
BESTÄNDIGKEITSLISTE FÜR DAS DOCKWEILER SCHLAUCHPROGRAMM



- Chemicals / Chemikalien**  
**A** - No effect / Keine Auswirkung  
**B** - Minor Effect-Good / Geringe Auswirkung  
**C** - Moderate Effect-Fair / Mäßige Auswirkung  
**D** - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
**1** - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
**2** - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                 | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|---------------------------|------|----------------|-----------|
| D                         |      |                |           |
| DIMETHYL PHTHALATE        | B    |                |           |
| DINITRO TOLUENE           | D    | D              |           |
| DIOCTYL PHTHALATE         | B    | C              |           |
| DIOCTYL SEBACATE          | B    | C              |           |
| DIOXANE                   | B    | D              |           |
| DIOXOLANE                 | B    | D              |           |
| DIPENTENE                 | D    | A              |           |
| DIPHENYL                  | D    | D              |           |
| DIPHENYL OXIDE            | D    | C              | A1        |
| DOW CHEMICAL 50-4         | A    |                |           |
| DOW CHEMICAL ET378        |      | D              |           |
| DOW CHEMICAL ET588        | A    |                |           |
| DOW CORNING-0003          | A    | C              |           |
| DOW CORNING-0004          | A    | C              |           |
| DOW CORNING-0005          | A    | C              |           |
| DOW CORNING-0011          | A    | C              |           |
| DOW CORNING-0033          | A    | C              |           |
| DOW CORNING-0044          | A    | C              |           |
| DOW CORNING-0055          | A    | C              |           |
| DOW CORNING-0200          | A    | C              |           |
| DOW CORNING-0220          | A    | C              |           |
| DOW CORNING-0510          | A    | C              |           |
| DOW CORNING-0550          | A    | C              |           |
| DOW CORNING-0704          | A    |                |           |
| DOW CORNING-0705          | A    |                |           |
| DOW CORNING-0710          | A    | C              |           |
| DOW CORNING-1208          | A    | C              |           |
| DOW CORNING-4050          | A    | C              |           |
| DOW CORNING-6620          | A    | C              |           |
| DOW CORNING-F60           | A    | C              |           |
| DOW CORNING-F61           | A    | B              |           |
| DOW CORNING-XF60          | A    | C              |           |
| DOW GUARD                 | A    | A              |           |
| DOWTHERM A OR E           | D    | D              |           |
| DOWTHERM OIL              | D    | B              |           |
| DOWTHERM209, 50% SOLUTION | A    | C              |           |
| DRINKING WATER            | A    | A              |           |
| DRY CLEANING FLUIDS       | D    | D              |           |
| DTE LIGHT OIL             | D    | D              |           |
| DYES                      |      |                |           |
|                           |      |                |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                         | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-----------------------------------|------|----------------|-----------|
| E                                 |      |                |           |
| ELCO 28-EP LUBRICANT              | D    | B              |           |
| EPICHLOROHYDRIN                   | B    | D              |           |
| EPOXY RESINS                      | A    |                |           |
| EPSOM SALTS ( MAGNESIUM SULFITE ) | A    | A              | A         |
| ESAM-6 FLUID                      | A    |                |           |
| ESSO FUEL 208                     | D    | B              |           |
| ESSO GOLDEN GASOLINE              | D    | D              |           |
| ESSO MOTOR OIL                    | D    | D              |           |
| ESSO TRANSMISSION FLUID (TYPE A)  | D    | D              |           |
| ESSO WS3812 (MIL-L-7808 A)        | D    | D              |           |
| ESSO XP90-EP LUBRICANT            | D    | D              |           |
| ESSTIC 42, 43                     | D    | B              |           |
| ETHANE                            | D    | D              | A         |
| ETHANOL                           | A    | A              |           |
| ETHANOLAMINE                      | B    | B              | A         |
| ETHER3                            | C    | D              | A         |
| ETHERS                            | C    | D              |           |
| ETHYL ACETATE                     | B    | B              | A         |
| ETHYL ACETOACETATE                | B    | B              |           |
| ETHYL ACRYLATE                    | B    | B              |           |
| ETHYL ACRYLIC ACID                | B    | D              |           |
| ETHYL BENZENE                     | D    | D              |           |
| ETHYL BENZOATE                    | D    | D              |           |
| ETHYL BROMIDE                     | D    |                |           |
| ETHYL CELLOSOLVE                  | B    | D              |           |
| ETHYL CELLULOSE                   | B    | C              |           |
| ETHYL CHLORIDE                    | A    | D              |           |
| ETHYL CHLOROCARBONATE             | D    | D              |           |
| ETHYL CHLOROFORMATE               | D    | D              |           |
| ETHYL CYCLOPENTANE                | D    | D              |           |
| ETHYL ETHER                       | C    | D              |           |
| ETHYL FORMATE                     | B    |                |           |
| ETHYL HEXANOL                     | A    | B              |           |
| ETHYL MERCAPTAN                   | D    | C              |           |
| ETHYL OXALATE                     | D    | D              |           |
| ETHYL PENTACHLOROBENZENE          | D    | D              |           |
| ETHYL SILICATE                    | A    |                |           |
| ETHYL SULFATE                     |      |                | A         |
| ETHYLENE                          |      |                |           |
| ETHYLENE CHLORIDE                 | D    | D              | A         |
| ETHYLENE CHLOROHYDRIN             | B    | C              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                        | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|--------------------------------------------------|------|----------------|-----------|
| E                                                |      |                |           |
| ETHYLENE DIAMINE                                 | A    | A              |           |
| ETHYLENE DIBROMIDE                               | C    | D              |           |
| ETHYLENE DICHLORIDE                              | C    | D              | A         |
| ETHYLENE GLYCOL                                  | A    | A              | A         |
| ETHYLENE OXIDE                                   | C    | D              | A         |
| ETHYLENE TRICHLORIDE                             | C    | D              |           |
| ETHYLMORPHOLENE STANNOUS OCTOATE (50/50 MIXTURE) | B    |                |           |
| F                                                |      |                |           |
| FATTY ACIDS                                      | D    | C              | A         |
| FC-43 HEPTACOSOFUOROTRI-BUTYLAMINE               | A    | A              |           |
| FC75 FLUOROCARBON                                | A    | A              |           |
| FERRIC CHLORIDE                                  | A    | B              | A         |
| FERRIC NITRATE                                   | A    | C              | A         |
| FERRIC SULFATE                                   | A    | B              | A         |
| FERROUS CHLORIDE                                 |      |                | A         |
| FERROUS SULFATE                                  | A    |                | A         |
| FISH OIL                                         | A    | A              |           |
| FLUOBORIC ACID                                   | A2   |                | A         |
| FLUORINATED CYCLIC ETHERS                        | A    |                |           |
| FLUORINE                                         | A1   | D              | A         |
| FLUORINE (LIQUID)                                | C    | D              |           |
| FLUOROBENZENE                                    | D    | D              |           |
| FLUOROCARBON OILS                                | A    |                |           |
| FLUOROLUBE                                       | A    | A              |           |
| FLUOSILICIC ACID                                 | A2   |                | A         |
| FORMALDEHYDE 100%                                | A    | B              | A         |
| FORMALDEHYDE 40%                                 | A    |                | A         |
| FORMIC ACID                                      | A    | B              | A         |
| FREON 11                                         | D    | D              | C         |
| FREON 112                                        | D    | D              |           |
| FREON 113                                        | D    | D              | A         |
| FREON 114                                        | A    | D              |           |
| FREON 114B2                                      | D    | D              |           |
| FREON 115                                        | A    | D              |           |
| FREON 12                                         | B    | D              | A         |
| FREON 12 AND ASTM-OIL #2 (50/50 MIXTURE)         | D    | D              |           |
| FREON 12 AND SUNISO 4G (50/50 MIXTURE)           | D    | D              |           |
| FREON 13                                         | A    | D              |           |
| FREON 13B1                                       | A    | D              |           |
| FREON 14                                         | A    | D              |           |
| FREON 142B                                       | A    |                |           |

**Chemicals / Chemikalien**  
**A** - No effect / Keine Auswirkung  
**B** - Minor Effect-Good / Geringe Auswirkung  
**C** - Moderate Effect-Fair / Mäßige Auswirkung  
**D** - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
**1** - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
**2** - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|------------------------------------------|------|----------------|-----------|
| F                                        |      |                |           |
| FREON 152A                               | A    |                |           |
| FREON 21                                 | D    | D              |           |
| FREON 218                                | A    |                |           |
| FREON 22                                 | A    | D              | A         |
| FREON 22 AND ASTM OIL #2 (50/50 MIXTURE) | D    | D              |           |
| FREON 31                                 | A    |                |           |
| FREON 32                                 | A    |                |           |
| FREON 502                                | A    |                |           |
| FREON BF                                 | D    | D              |           |
| FREON C316                               | A    |                |           |
| FREON C318                               | A    |                |           |
| FREON MF                                 | D    | D              |           |
| FREON PCA                                | D    | D              |           |
| FREON TA                                 | A    | A              |           |
| FREON TC                                 | B    | D              |           |
| FREON TF                                 | D    | D              | D         |
| FREON TMC                                | B    | C              |           |
| FREON T-P35                              | A    | A              |           |
| FREON T-WD602                            | B    | D              |           |
| FRUIT JUICE                              |      |                | A         |
| FUEL OILS                                | D    | C              | A         |
| FUEL OILS #6                             | D    | A              |           |
| FUEL OILS ACIDIC                         | D    | A              |           |
| FUFURAL                                  | B    | D              |           |
| FUFURALDEHYDE                            | B    | D              |           |
| FUMARIC ACID                             |      | B              |           |
| FUMING SULPHURIC ACID (20/25% OLEUM)     | D    | D              |           |
| FURAN (FUFURAN)                          | C    |                |           |
| FURFURAL                                 | B    | D              | A         |
| FURYL CARBINOL                           | B    | D              |           |
| FYRQUEL 90, 100, 150, 220, 300, 500      | A    | A              |           |
| FYRQUEL A60                              | B    | C              |           |
| G                                        |      |                |           |
| GALLIC ACID                              | B    |                | A         |
| GASOLINE                                 | D    | D              | A         |
| GELATIN                                  | A    | A              | A         |
| GLAUBER'S SALT                           | B    |                |           |
| GLUCOSE                                  | A    | A              | A         |
| GLUE (DEPENDING ON TYPE)                 | A    | A              |           |
| GLUE, P. V. A.                           | A    | A              | A         |
| GLYCERIN                                 | A    | A              | A         |

**Chemicals / Chemikalien**  
**A** - No effect / Keine Auswirkung  
**B** - Minor Effect-Good / Geringe Auswirkung  
**C** - Moderate Effect-Fair / Mäßige Auswirkung  
**D** - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
**1** - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
**2** - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|------------------------------------------|------|----------------|-----------|
| G                                        |      |                |           |
| GLYCERINE-GLYCEROL                       | A    | A              |           |
| GLYCOLIC ACID                            | A    | A              | A         |
| GLYCOLS                                  | A    | A              |           |
| GOLD MONOCYANIDE                         |      |                | D         |
| GRAPE JUICE                              |      |                | D         |
| GREASE                                   |      |                | A         |
| GREASE LIGHT                             | D    | D              |           |
| GREEN SULPHATE LIQUOR                    | A    | A              |           |
| GRILING BRAKE FLUID                      | A    |                |           |
| GULF ENDURANCE OILS                      | D    | D              |           |
| GULF FR FLUIDS (EMULSION)                | D    | D              |           |
| GULF FRG-FLUIDS                          | A    | A              |           |
| GULF FRP-FLUIDS                          | B    | A              |           |
| GULF HARMONY OILS                        | D    | D              |           |
| GULF HIGH TEMPERATURE GREASE             | D    | D              |           |
| GULF LESION OILS                         | D    | D              |           |
| GULF PARAMOUNT OILS                      | D    | D              |           |
| GULF SECURITY OILS                       | D    | D              |           |
| GULFCROWN GREASE                         | D    | D              |           |
| H                                        |      |                |           |
| HALOTHANE                                | D    | D              |           |
| HALOWAX OIL                              | D    | D              |           |
| HANNIFIN LUBE A                          | D    | B              |           |
| HEAVY WATER                              | A    | A              |           |
| HEF-2 (HIGH ENERGY FUEL)                 | D    | D              |           |
| HELIUM                                   | A    | A              |           |
| HEPTANE                                  | D    | D              | A         |
| HEXANE                                   | D    | D              | A         |
| HIGH VISCOSITY LUBRICANT, H2             | A    | A              |           |
| HIGH VISCOSITY LUBRICANT, U4             | A    | A              |           |
| HILO MS #1                               | A    | C              |           |
| HONEY                                    |      |                | A         |
| HOUGHTO-SAFE 1010, PHOSPHATE ESTER       | A    | C              |           |
| HOUGHTO-SAFE 1055, PHOSPHATE ESTER       | A    | C              |           |
| HOUGHTO-SAFE 1120, PHOSPHATE ESTER       | A    | C              |           |
| HOUGHTO-SAFE 271 (WATER AND GLYCOL BASE) | A    | B              |           |
| HOUGHTO-SAFE 5040 (WATER/OIL EMULSION)   | D    | C              |           |
| HOUGHTO-SAFE 620 (WATER/GLYCOL)          | A    | B              |           |
| HYDRAULIC OIL ( PETRO )                  | D    | C              | A         |
| HYDRAULIC OIL ( SYNTHETIC )              |      |                | A         |
| HYDRAZINE                                | A    | C              | C         |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                            | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|--------------------------------------|------|----------------|-----------|
| H                                    |      |                |           |
| HYDROBROMIC ACID 100%                | A    | D              | A         |
| HYDROBROMIC ACID 20%                 | A    | D              |           |
| HYDROBROMIC ACID 40%                 | A    | D              |           |
| HYDROCARBONS (SATURDATED)            | D    | D              |           |
| HYDROCHLORIC ACID 100%               | C    | D              | A         |
| HYDROCHLORIC ACID 20%                |      |                | A         |
| HYDROCHLORIC ACID 3 MOLAR            | A    | D              |           |
| HYDROCHLORIC ACID 37%                | A    | B              | A         |
| HYDROCHLORIC ACID CONCENTRATED       | C    | D              |           |
| HYDROCHLORIC ACID HOT 37%            | C    | D              |           |
| HYDROCHLORIC ACID, DRY GAS           |      |                | A         |
| HYDROCYANIC ACID                     | A    | C              | A         |
| HYDRO-DRIVE, MIH-50 (PETROLEUM BASE) | D    | B              |           |
| HYDRO-DRIVE, MIH-10 (PETROLEUM BASE) | D    | B              |           |
| HYDROFLUORIC ACID 020%               | A1   | D              | A         |
| HYDROFLUORIC ACID 050%               | A1   | D              | A         |
| HYDROFLUORIC ACID 075%               | C    | D              | A         |
| HYDROFLUORIC ACID 100%               | C    | D              | A         |
| HYDROFLUORIC ACID 65% MAX.COLD       | A    | D              |           |
| HYDROFLUORIC ACID 65% MAX.HOT        | D    | D              |           |
| HYDROFLUORIC ACID 65% MIN.COLD       | C    | D              |           |
| HYDROFLUORIC ACID 65% MIN.HOT        | D    | D              |           |
| HYDROFLUOSILICIC ACID 020%           | A    |                | A         |
| HYDROFLUOSILICIC ACID 100%           | A    | D              | A         |
| HYDROGEN 90% (1)                     | C    | B              |           |
| HYDROGEN GAS                         | A    | C              | A         |
| HYDROGEN GAS, COLD                   | A    | C              |           |
| HYDROGEN GAS, HOT                    | A    | C              |           |
| HYDROGEN PEROXIDE 010%               |      | B              | A         |
| HYDROGEN PEROXIDE 030%               |      | B              | A         |
| HYDROGEN PEROXIDE 050%               |      | B              | A         |
| HYDROGEN PEROXIDE 100%               | A    | B              | A         |
| HYDROGEN SULFIDE ( AQUA )            | A    | C              | A         |
| HYDROGEN SULFIDE ( DRY )             | A    | C              | A         |
| HYDROGEN SULFIDE DRY, COLD           | A    | C              |           |
| HYDROGEN SULFIDE DRY, HOT            | A    | C              |           |
| HYDROGEN SULFIDE WET, COLD           | A    | C              |           |
| HYDROGEN SULFIDE WET, HOT            | A    | C              |           |
| HYDROLUBE-WATER/ETHYLENE GLYCOL      | A    | B              |           |
| HYDROQUINONE                         | D    |                |           |
| HYDROXYACETIC ACID 70%               | A    |                |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|--------------------------|------|----------------|-----------|
| H                        |      |                |           |
| HYDYNE                   | A    | D              |           |
| HYJET                    | A    |                |           |
| HYJET III                | A    |                |           |
| HYJET S                  | A    |                |           |
| HYJET W                  | A    |                |           |
| HYPOCHLOROUS ACID        | B    |                |           |
| I                        |      |                |           |
| INDUSTRON FF44           | D    | D              |           |
| INDUSTRON FF48           | D    | D              |           |
| INDUSTRON FF53           | D    | D              |           |
| INDUSTRON FF80           | D    | D              |           |
| INK                      |      |                | D         |
| IODINE                   | B    |                | A         |
| IODINE ( IN ALCOHOL )    |      |                |           |
| IODINE PENTAFLUORIDE     | D    | D              |           |
| ODOFORM                  | A    |                | C         |
| ISO-BUTYL N-BUTYRATE     | A    |                |           |
| ISODODECANE              | D    |                |           |
| ISO-OCTANE               | D    | D              |           |
| ISOPHORONE (KETONE)      | A    | D              |           |
| ISOPROPANOL              | A    | A              |           |
| ISOPROPYL ACETATE        | B    | D              | A         |
| ISOPROPYL CHLORIDE       | D    | D              |           |
| ISOPROPYL ETHER          | D    | D              | A1        |
| ISOTANE                  |      |                |           |
| J                        |      |                |           |
| JET FUEL ( JP3, -4, -5 ) | D    | D              | A         |
| JP 3 (MIL-J-5624)        | D    | D              |           |
| JP 4 (MIL-J-5624)        | D    | D              |           |
| JP 5 (MIL-J-5624)        | D    | D              |           |
| JP 6 (MIL-J-25656)       | D    | D              |           |
| JP X (MIL-F-25604)       | D    | D              |           |
| K                        |      |                |           |
| KEL F LIQUIDS            | A    | A              |           |
| KEROSENE                 | D    | D              | A         |
| KETONES                  | D    |                | A         |
| KEYSTONE #87HX-GREASE    | D    | D              |           |
| L                        |      |                |           |
| LACQUER SOLVENTS         | D    | D              |           |
| LACQUER THINNERS         | D    | D              | A         |
| LACTAMS-AMINO ACIDS      | B    |                |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                      | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|------------------------------------------------|------|----------------|-----------|
| L                                              |      |                |           |
| LACTIC ACID                                    | A    | A              | A         |
| LACTIC ACID, COLD                              | A    |                |           |
| LACTIC ACID, HOT                               | D    |                |           |
| LARD                                           | D    | B              | A         |
| LATEX                                          | A    |                | A         |
| LAVENDER OIL                                   | D    | D              |           |
| LEAD ACETATE                                   | A    | D              | A         |
| LEAD NITRATE                                   | A    | B              |           |
| LEAD SULFAMATE                                 | A    | B              | A1        |
| LEHIGH X1169                                   | D    | D              |           |
| LEHIGH X1170                                   | D    | D              |           |
| LIGROIN                                        | D    | D              |           |
| LIME                                           | D    |                | A1        |
| LIME BLEACH                                    | A    | B              |           |
| LIME SULPHUR                                   | A    | A              |           |
| LINDOL, HYDRAULIC FLUID (PHOSPHATE ESTER TYPE) | A    | C              |           |
| LINOLEIC ACID                                  | D    | B              |           |
| LINSEED OIL                                    | C    | A              |           |
| LIQUID OXYGEN                                  | D    | D              |           |
| LIQUID PETROLEUM GAS (LPG)                     | D    | C              |           |
| LIQUIMOLY                                      | D    | D              |           |
| LUBRICANTS                                     | D    | D              | A         |
| LUBRICATING OILS, DI-ESTER                     | D    | D              |           |
| LUBRICATING OILS, PETROLEUM BASE               | D    | D              |           |
| LUBRICATING OILS, SAE 10, 20, 30, 40, 50       | D    | D              |           |
| LYE SOLUTIONS                                  | A    | B              |           |
| M                                              |      |                |           |
| MAGNESIUM CARBONATE                            | A    |                | A1        |
| MAGNESIUM CHLORIDE                             | A    | A              | A         |
| MAGNESIUM HYDROXIDE                            | A    | A              | A         |
| MAGNESIUM NITRATE                              | A    |                | A         |
| MAGNESIUM OXIDE                                |      |                |           |
| MAGNESIUM SALT                                 | A    | A              |           |
| MAGNESIUM SULFATE                              | A    | A              | A         |
| MAGNESIUM SULPHITE                             | A    | A              |           |
| MALATHION                                      | D    | D              |           |
| MALEIC ACID                                    | D    |                | A         |
| MALEIC ANHYDRIDE                               | D    |                |           |
| MALIC ACID                                     | D    | B              | A         |
| MASH                                           | A    |                |           |
| MAYONNAISE                                     |      |                | D         |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                     | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-------------------------------|------|----------------|-----------|
| M                             |      |                |           |
| MCS 312                       | D    | A              |           |
| MCS 352                       | A    | C              |           |
| MCS 463                       | A    | C              |           |
| MELAMINE                      | A    |                | A         |
| MERCURIC CHLORIDE ( DILUTE )  | A    |                | A         |
| MERCURIC CYANIDE              |      |                | A         |
| MERCURY                       | A    |                | A         |
| MERCURY VAPORS                | A    |                |           |
| MESITYL OXYDE (KETONE)        | B    | D              |           |
| METHANE                       | D    | D              |           |
| METHANOL                      | A    | A              |           |
| METHYL ACETATE                | B    | D              | A         |
| METHYL ACETOACETATE           | B    | B              |           |
| METHYL ACETONE                |      |                | A         |
| METHYL ACRYLATE               | B    | D              |           |
| METHYL BENZOATE               | D    | D              |           |
| METHYL BROMIDE                | D    |                | A         |
| METHYL BUTYL KETONE           | A    | D              |           |
| METHYL CARBONATE              | D    | D              |           |
| METHYL CELLOSOLVE             | B    | D              |           |
| METHYL CELLULOSE              | B    | B              |           |
| METHYL CHLORIDE               | C    | D              | A         |
| METHYL CHLOROFORMATE          | D    | D              |           |
| METHYL COLLOSOLVE             | A    | D              | A         |
| METHYL CYCLOPENTHANE          | D    | D              |           |
| METHYL D-BROMIDE              |      | D              |           |
| METHYL DICHLORIDE             | D    |                |           |
| METHYL ETHER                  | A    | A              |           |
| METHYL ETHYL KETONE (MEK)     | A    | D              | A         |
| METHYL ETHYL KETONE PEROXIDE  | D    | B              |           |
| METHYL FORMAT                 | B    | B              |           |
| METHYL ISOBUTYL KETONE (MIBK) | C    | D              | A         |
| METHYL ISOPROPYL KETONE       | B    | D              |           |
| METHYL METHACRYLATE           | D    | C              |           |
| METHYL OLEATE                 | B    |                |           |
| METHYL SALICYLATE             | B    |                |           |
| METHYLACRYLIC ACID            | B    | D              |           |
| METHYLAMINE                   | A1   |                | A         |
| METHYLENE CHLORIDE            | D    | D              | A         |
| METHYLENE DICHLORIDE          | D    | D              |           |
| MIL-A-6091                    | A    | A              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals    | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|--------------|------|----------------|-----------|
| M            |      |                |           |
| MIL-A-8243B  | A    | B              |           |
| MIL-C-4339C  | D    | C              |           |
| MIL-C-5545A  | D    | D              |           |
| MIL-C-6529C  | D    | D              |           |
| MIL-C-8188C  | D    | D              |           |
| MIL-E-9500   | A    | A              |           |
| MIL-F-16884  | D    | D              |           |
| MIL-F-16929A | D    | C              |           |
| MIL-F-17111  | D    | D              |           |
| MIL-F-19605  | D    | D              |           |
| MIL-F-25172  | D    | D              |           |
| MIL-F-25524A | D    | D              |           |
| MIL-F-25558B | D    | D              |           |
| MIL-F-25576C | D    | D              |           |
| MIL-F-25656B | D    | D              |           |
| MIL-F-5566   | A    | A              |           |
| MIL-F-5602   | D    | C              |           |
| MIL-F-7024A  | D    | D              |           |
| MIL-G-10924B | D    | D              |           |
| MIL-G-15793  | D    | D              |           |
| MIL-G-18709A | D    | C              |           |
| MIL-G-2108   | D    | C              |           |
| MIL-G-21568A | A    | D              |           |
| MIL-G-23827A | D    | C              |           |
| MIL-G-25013D | D    | D              |           |
| MIL-G-25537A | D    | D              |           |
| MIL-G-25760A | D    | D              |           |
| MIL-G-27343  | A    | D              |           |
| MIL-G-27617  | A    | D              |           |
| MIL-G-3278   | D    | D              |           |
| MIL-G-4343B  | C    | D              |           |
| MIL-G-5572   | D    | D              |           |
| MIL-G-7118A  | D    | D              |           |
| MIL-G-7187   | D    | D              |           |
| MIL-G-7421A  | D    | D              |           |
| MIL-G-7711A  | D    | C              |           |
| MIL-H-13862  | D    | C              |           |
| MIL-H-13866A | D    | C              |           |
| MIL-H-13910B | A    | D              |           |
| MIL-H-13919A | D    | C              |           |
| MIL-H-19457B | A    | D              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals         | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-------------------|------|----------------|-----------|
| M                 |      |                |           |
| MIL-H-22072       | A    | B              |           |
| MIL-H-22251       | A    | D              |           |
| MIL-H-25598       | D    | C              |           |
| MIL-H-27601A      | D    | D              |           |
| MIL-H-46001A      | D    | C              |           |
| MIL-H-46004       | D    | C              |           |
| MIL-H-5559A       | A    | B              |           |
| MIL-H-5606B       | D    | D              |           |
| MIL-H-6083C       | D    | D              |           |
| MIL-H-7083        | A    | B              |           |
| MIL-H-7644        | A    | D              |           |
| MIL-H-81019B      | D    | C              |           |
| MIL-H-83282       | D    | D              |           |
| MIL-H-8446B       | D    | D              |           |
| MIL-I-27686D      | A    | B              |           |
| MIL-I-8660B       | A    | D              |           |
| MIL-J-5161F       | D    | D              |           |
| MIL-J-5624G, JP-3 | D    | D              |           |
| MIL-J-5624G, JP-4 | D    | D              |           |
| MIL-J-5624G, JP-5 | D    | D              |           |
| MILK              | A    | A              | A         |
| MIL-L-10295A      | D    | C              |           |
| MIL-L-10324A      | D    | C              |           |
| MIL-L-11734B      | D    | C              |           |
| MIL-L-14107B      | D    | D              |           |
| MIL-L-15016       | D    | D              |           |
| MIL-L-15017       | D    | D              |           |
| MIL-L-15018B      | D    | C              |           |
| MIL-L-15019C      | D    | C              |           |
| MIL-L-15719A      | B    | D              |           |
| MIL-L-16958A      | D    | C              |           |
| MIL-L-17331B      | D    | D              |           |
| MIL-L-17353A      | D    | C              |           |
| MIL-L-17672B      | D    | C              |           |
| MIL-L-18486A      | D    | C              |           |
| MIL-L-19701       | D    | C              |           |
| MIL-L-2104B       | D    | D              |           |
| MIL-L-2105B       | D    | C              |           |
| MIL-L-21260       | D    | D              |           |
| MIL-L-22396       | D    | C              |           |
| MIL-L-23699A      | D    | D              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                   | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-----------------------------|------|----------------|-----------|
| M                           |      |                |           |
| MIL-L-25336B                | D    | C              |           |
| MIL-L-25681C                | A    | D              |           |
| MIL-L-25968                 | D    | C              |           |
| MIL-L-26087A                | D    | C              |           |
| MIL-L-27694A                | A    | D              |           |
| MIL-L-3150A                 | D    | D              |           |
| MIL-L-3503                  | D    | D              |           |
| MIL-L-3545B                 | D    | D              |           |
| MIL-L-46000A                | D    | C              |           |
| MIL-L-46002                 | D    | C              |           |
| MIL-L-5020A                 | D    | D              |           |
| MIL-L-6081C                 | D    | D              |           |
| MIL-L-6085A                 | D    | D              |           |
| MIL-L-6086B                 | D    | C              |           |
| MIL--L-6387A                | D    | D              |           |
| MIL-L-644B                  | C    | C              |           |
| MIL-L-6482C                 | D    | C              |           |
| MIL-L-7645                  | D    | D              |           |
| MIL-L-7808F                 | D    | D              |           |
| MIL-L-7870A                 | D    | D              |           |
| MIL-L-8383B                 | D    | C              |           |
| MIL-L-9000F                 | D    | D              |           |
| MIL-L-9236B                 | D    | D              |           |
| MIL-O-11773                 | D    | C              |           |
| MIL-P-12098                 | A    | D              |           |
| MIL-P-27402                 | A    | D              |           |
| MIL-P-46046A                | A    | D              |           |
| MIL-S-3136B, TYPE I FUEL    | D    | D              |           |
| MIL-S-3136B, TYPE II FUEL   | D    | D              |           |
| MIL-S-3136B, TYPE III       | D    | D              |           |
| MIL-S-3136B, TYPE IV        | D    | C              |           |
| MIL-S-3136B, TYPE V         | D    | C              |           |
| MIL-S-3136B, TYPE VI        | D    | C              |           |
| MIL-S-3136B, TYPE VII       | D    | D              |           |
| MIL-S-81087                 | A    | D              |           |
| MIL-T-9188B                 | A    | D              |           |
| MINERAL OILS                | D    | B              |           |
| MOBIL 24 DTE                | D    | D              |           |
| MOBIL DELVAC 1100,1110,1130 | D    | D              |           |
| MOBIL HF                    | D    |                |           |
| MOBIL NYVAC 20 AND 30       | A    | A              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                     | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-----------------------------------------------|------|----------------|-----------|
| M                                             |      |                |           |
| MOBIL OIL SAE20                               | D    | D              |           |
| MOBIL VELOCITE C                              | D    | D              |           |
| MOBILGAS WA200, TYPE A, AUTOMATIC TRANS.FLUID | D    | D              |           |
| MOBILTHERM600                                 | D    | D              |           |
| MOBILUX                                       | D    | D              |           |
| MOLASSES                                      |      |                | A         |
| MONO BROMOBENZENE                             | D    | D              |           |
| MONO CHLOROBENZENE                            | D    | D              |           |
| MONO ETHANOLAMINE                             | B    | B              |           |
| MONOMERTHYL ANILINE                           |      |                |           |
| MONOMETHYL HYDRAZINE                          | A    | D              |           |
| MONOMETHYLETHER                               | A    |                |           |
| MONOTROTOLUENE & DINITROTOLUENE (40-60 MIX)   | D    | D              |           |
| MONOVINYL ACETHYLENE                          | A    | B              |           |
| MOPAR BRAKE FLUID                             | A    | C              |           |
| MUSTARD                                       |      |                | A         |
| MUSTARD GAS                                   | A    | A              |           |
| N                                             |      |                |           |
| NAPHTA                                        | D    | D              | A         |
| NAPHTHALENE                                   | D    | D              | A         |
| NAPTHENIC ACID                                | D    | D              |           |
| NATURAL GAS                                   | D    | A              |           |
| NEATSFOOT OIL                                 | B    | B              |           |
| NEON                                          | A    | A              |           |
| NEVILLE ACID                                  | B    | D              |           |
| N-HEPTANE                                     | D    | D              |           |
| N-HEXALDEHYDE                                 | A    | B              |           |
| N-HEXANE-1                                    | D    | D              |           |
| NICKEL ACETATE                                | A    | D              |           |
| NICKEL CHLORIDE                               | A    | A              | A         |
| NICKEL SALTS                                  | A    | A              |           |
| NICKEL SULFATE                                | A    | A              | A         |
| NITER CAKE                                    | A    | A              |           |
| NITRATING ACID (<15% H2SO4 )                  |      |                | A         |
| NITRATING ACID (<15% HNO3 )                   |      |                | A         |
| NITRATING ACID (>15% H2SO4 )                  |      |                | A         |
| NITRIC ACID (1) 3 MOLAR                       | B    | D              |           |
| NITRIC ACID (1) CONCENTRATE                   | D    | D              | A         |
| NITRIC ACID (1) INHIBITED RED FUMING (IRFNA)  | D    | D              |           |
| NITRIC ACID (1) RED FUMING (RFNA)             | D    | D              |           |
| NITRIC ACID 20%                               | B    | D              | A         |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                         | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-----------------------------------|------|----------------|-----------|
| N                                 |      |                |           |
| NITRIC ACID 50%                   | D    | D              | A         |
| NITRIC ACID 5-10%                 | B    | C              | A         |
| NITRIC ACID DILUTE                | B    | B              |           |
| NITROBENZENE                      | D    | D              | A         |
| NITROBENZENE                      | D    | D              |           |
| NITROBENZINE                      | C    |                |           |
| NITROETHANE                       | B    | D              |           |
| NITROGEN                          | A    | A              |           |
| NITROGEN (TEXTROXIDE) (N2O4) (1)  | D    | D              |           |
| NITROMETHANE                      | B    | D              |           |
| NITROPROPANE                      | B    | D              |           |
| NITROUS ACID                      | A    |                | A         |
| N-OCTANE                          | D    | D              |           |
| N-PENTANE                         | D    | D              |           |
| N-PROPYL ACETONE                  | A    | D              |           |
| O                                 |      |                |           |
| O-A-548A                          | A    | B              |           |
| OCTACHLOROTOLUENE                 | D    | D              |           |
| OCTADECANE                        | D    | D              |           |
| O-DICHLOROBENZENE                 | D    | D              |           |
| OILS ( CONT'D ) :MINERAL          | D    | C              | A         |
| OILS ( CONT'D ) :OILS ( CONT'D ): |      |                |           |
| OILS ( CONT'D ) :OLIVE            | B    | D              | A1        |
| OILS ( CONT'D ) :ORANGE           |      | D              |           |
| OILS ( CONT'D ) :PALM             |      |                |           |
| OILS ( CONT'D ) :PEANUT           | C    | A              | A         |
| OILS ( CONT'D ) :PEPPERMINT       |      |                |           |
| OILS ( CONT'D ) :PINE             | D    | D              | A         |
| OILS ( CONT'D ) :RAPESEED         | A    | D              |           |
| OILS ( CONT'D ) :ROSin            |      |                | A         |
| OILS ( CONT'D ) :SESAME SEED      |      |                | A         |
| OILS ( CONT'D ) :SILICONE         | A    | C              | A         |
| OILS ( CONT'D ) :SOYBEAN          | C    | A              | A         |
| OILS ( CONT'D ) :SPERM            |      |                |           |
| OILS ( CONT'D ) :TANNING          |      |                |           |
| OILS ( CONT'D ) :TURBINE          | D    | D              | A         |
| OILS :ANILINE                     | B    | D              | A         |
| OILS :ANISE                       |      |                |           |
| OILS :BAY                         |      |                |           |
| OILS :BONE                        |      |                |           |
| OILS :CASTOR                      | B    | A              | A         |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                             | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|---------------------------------------|------|----------------|-----------|
| O                                     |      |                |           |
| OILS :CINNAMON                        |      |                |           |
| OILS :CITRIC                          |      |                | D         |
| OILS :CLOVE                           |      |                |           |
| OILS :COCOA NUT                       | C    | A              | A         |
| OILS :COD LIVER                       | A    | B              | A         |
| OILS :CORN                            | C    | A              | A         |
| OILS :COTTON SEED                     | C    | A              | A         |
| OILS :CREOSOTE                        | D    | D              | A         |
| OILS :DIESEL FUEL ( 20,30,40,50 )     | D    | D              | A         |
| OILS :FUEL (1,2,3,5A,6 )              | D    | C              | A         |
| OILS :GINGER                          | A    |                |           |
| OILS :HYDRAULIC ( SEE HYDRAULIC OIL ) |      |                |           |
| OILS :LINSEED                         | C    | A              | A         |
| OLEIC ACID                            | B    | D              | A         |
| OLEUM (FUMING SULFURIC ACID)          | D    | D              |           |
| OLEUM 100%                            | D    | D              | A         |
| OLEUM 25%                             | D    | D              | A         |
| OLEUM SPIRITS                         | D    | D              |           |
| OLIVE OIL                             | B    | D              |           |
| ORONITE 8200                          | D    | D              |           |
| ORONITE 8515                          | D    | D              |           |
| ORTHOCHLOROETHYLBENZENE               | D    | D              |           |
| ORTHO-DICHLOROBENZENE                 | D    | D              |           |
| OS45 TYPE III (OS45)                  | D    | D              |           |
| OS45 TYPE IV (OS45-1)                 | D    | D              |           |
| OS70                                  | D    | D              |           |
| O-T-634B                              | D    | D              |           |
| OXALIC ACID ( COLD )                  | A    | B              | A1        |
| OXYGEN, COLD                          | A    | A              |           |
| OXYGEN, COLD 200-400°F                | D    | B              |           |
| OZONE                                 | A    | A              |           |
| P                                     |      |                |           |
| PAINT THINNER DUCO                    | D    | D              |           |
| PALMITIC ACID                         | B    | D              |           |
| PARA-DICHLOROBENZENE                  | D    | D              |           |
| PARAFFIN                              | D    |                | A         |
| PAR-AL-KETONE                         | D    | D              |           |
| PARKER O LUBE                         | D    | B              |           |
| PATASH                                |      |                |           |
| P-CYMENE                              | D    | D              |           |
| P-D-680                               | D    | D              |           |

RESISTANCE LIST DOCKWEILER HOSES  
BESTÄNDIGKEITSLISTE FÜR DAS DOCKWEILER SCHLAUCHPROGRAMM

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                         | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|---------------------------------------------------|------|----------------|-----------|
| P                                                 |      |                |           |
| P-DICHLOROBENZENE                                 | D    | D              |           |
| PEANUT OIL                                        | C    | A              |           |
| PENTANE                                           | D    | D              | A         |
| PENTANE 2 METHYL                                  | D    | D              |           |
| PENTANE, 2-4 DIMETHYL                             | D    | D              |           |
| PENTANE, 3 METHYL                                 | D    | D              |           |
| PERCHLORIC ACID                                   | B    | D              |           |
| PERCHLOROETHYLENE                                 | D    | D              | A         |
| PETROLEUM OIL, ABOVE 250°F                        | D    | D              |           |
| PETROLEUM OIL, BELOW 250°F                        | D    | B              |           |
| PETROLEUM OIL, CRUDE                              | D    | D              |           |
| PHENOL                                            | B    | D              |           |
| PHENOL ( CARBOLIC ACID )                          | B    | D              | A         |
| PHENOL 10%                                        | B    | D              | A         |
| PHENOL, 70%/30%/H2O                               | D    | D              |           |
| PHENOL, 85%/15% H2O                               | D    | D              |           |
| PHENYL ETHYL ETHER                                | D    | D              |           |
| PHENYL HYDRAZINE                                  | D    |                |           |
| PHENYLBENZENE                                     | D    | D              |           |
| PHORONE                                           | B    | D              |           |
| PHOSPHORIC ACID ( CRUDE )                         | B    | C              | A         |
| PHOSPHORIC ACID ( MOLTEN )                        |      |                |           |
| PHOSPHORIC ACID < 40%                             | B    | D              | A         |
| PHOSPHORIC ACID > 40%                             | B    | C              | A         |
| PHOSPHORIC ACID 20%                               | A    | B              |           |
| PHOSPHORIC ACID 45%                               | B    | D              |           |
| PHOSPHORIC ACID ANHYDRIDE                         | B    |                |           |
| PHOSPHORIC ACID, 3 MOLAR                          | A    | B              |           |
| PHOSPHORIC ACID, CONCENTRATED                     | B    | C              |           |
| PHOSPHOROUS TRICHLORIDE                           | A    |                |           |
| PHOTOGRAPHIC DEVELOPER                            | B    | A              | A         |
| PHTHALIC ANHYDRIDE                                | A    |                | A         |
| PICKLING SOLUTION                                 | C    | D              |           |
| PICRIC ACID                                       | B    | D              | A         |
| PICRIC ACID H2O SOLUTION                          | B    | D              |           |
| PICRIC ACID MOLTEN                                | B    | D              |           |
| PINE OIL                                          | D    | D              |           |
| PINENE                                            | D    | D              |           |
| PIPERIDINE                                        | D    | D              |           |
| PLATING SOLUTIONS ( CONT. ) :ACID 75° F           |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :ACID CHLORIDE 140° F |      |                | A         |

RESISTANCE LIST DOCKWEILER HOSES  
BESTÄNDIGKEITSLISTE FÜR DAS DOCKWEILER SCHLAUCHPROGRAMM



Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                                     | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|---------------------------------------------------------------|------|----------------|-----------|
| P                                                             |      |                |           |
| PLATING SOLUTIONS ( CONT. ) :ACID FLUOBORATE BATH R.T.        |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :ACID SULFATE BATH 150° F         |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :ALKALINE CYANIDE BATH R.T.       |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :BARREL CHROME BATH 95° F         |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :BLACK CHROME BATH 115° F         |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :COPPER ( ELECTROLESS )           |      |                | A         |
| "PLATING SOLUTIONS ( CONT. ) :COPPER FLUOBORATE BATH 120F"    |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :COPPER PLATING ( ACID )          |      |                |           |
| PLATING SOLUTIONS ( CONT. ) :COPPER PLATING ( MISC. )         |      |                |           |
| PLATING SOLUTIONS ( CONT. ) :COPPER PLATING ( SYANIDE )       |      |                |           |
| PLATING SOLUTIONS ( CONT. ) :COPPER PYROPHOSPHATE             |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :COPPER STRIKE BATH 120° F        |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :COPPER SULFATE BATH R.T.         |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :CYANIDE 150° F                   |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :ELECTROLESS 200° F               |      |                | A         |
| "PLATING SOLUTIONS ( CONT. ) :FERROUS AN SULFATE BATH 150° F" |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :FERROUS CHLORIDE BATH 190° F     |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :FERROUS SULFATE BATH 150° F      |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :FLUOBORATE 100-170° F            |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :FLUOBORATE BATH 145° F           |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :FLUORIDE BATH 130° F             |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :GOLD PLATING                     |      |                |           |
| PLATING SOLUTIONS ( CONT. ) :HIGH CHLORIDE 130-160° F         |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :HIGH SPEED BATH 180° F           |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :INDIUM SULFAMATE PLATING R.T.    |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :IRON PLATING                     |      |                |           |
| PLATING SOLUTIONS ( CONT. ) :LEAD FLOBORATE PLATING           |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :NEUTRAL 75° F                    |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :NICKEL PLATING                   |      |                |           |
| PLATING SOLUTIONS ( CONT. ) :PLATING SOLUTIONS ( CONT. )      |      |                |           |
| PLATING SOLUTIONS ( CONT. ) :RHODIUM PLATING 120° F           | A    |                | A         |
| PLATING SOLUTIONS ( CONT. ) :ROCHELLE SALT BATH 150° F        |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :SILVER PLATING 80-120° F         | A    |                | A         |
| PLATING SOLUTIONS ( CONT. ) :SUFAMATE 140° F                  |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :SULFAMATE 100-140° F             |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :TIN-FLURORATE PLATING 100° F     |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :TIN-LEAD PLATING 100° F          |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :WATTS TYPE 115-160° F            |      |                | A         |
| PLATING SOLUTIONS ( CONT. ) :ZINC PLATING                     |      |                |           |
| PLATING SOLUTIONS : OTHERS                                    | A    | D              |           |
| PLATING SOLUTIONS :ANTIMON PLATING 130° F                     |      |                | A         |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                       | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-------------------------------------------------|------|----------------|-----------|
| P                                               |      |                |           |
| PLATING SOLUTIONS :ARSENIC PLATING 110° F       |      |                | A         |
| PLATING SOLUTIONS :BRASS PLATING                |      |                |           |
| PLATING SOLUTIONS :BRONZE PLATING               |      |                |           |
| PLATING SOLUTIONS :CADMIUM PLATING              |      |                |           |
| PLATING SOLUTIONS :CHROME                       | A    | D              |           |
| PLATING SOLUTIONS :CHROMIUM PLATING             |      |                |           |
| PLATING SOLUTIONS :CU-CD BRONZE BATH R.T.       | A    |                | A         |
| PLATING SOLUTIONS :CU-SN BRONZE BATH 160° F     | A    |                | A         |
| PLATING SOLUTIONS :CU-ZN BRONZE BATH 100° F     |      |                | A         |
| PLATING SOLUTIONS :CYANIDE BATH 90° F           |      |                | A         |
| PLATING SOLUTIONS :FLUOBORATE BATH 100° F       |      |                | A         |
| PLATING SOLUTIONS :FLUOSILICATE BATH 95° F      |      |                | A         |
| PLATING SOLUTIONS :HIGH SPEED BRASS BATH 110° F |      |                | A         |
| PLATING SOLUTIONS :REGULAR BRASS BATH 100° F    |      |                | A         |
| PNEUMATIC SERVICE                               | A    | D              |           |
| POLYVINYL ACETATE EMULSION                      | A    | D              |           |
| POTASSIUM ACETATE                               | A    | D              |           |
| POTASSIUM BICARBONATE                           |      |                | A         |
| POTASSIUM BROMIDE                               | A    |                | A         |
| POTASSIUM CHLORATE                              | A    |                | A         |
| POTASSIUM CHLORIDE                              | A    | A              | A         |
| POTASSIUM CHROMATE                              | A    |                | A         |
| POTASSIUM CUPRO CYANIDE                         | A    | A              |           |
| POTASSIUM CYANIDE                               | A    | A              |           |
| POTASSIUM DICHROMATE                            | A    | A              |           |
| POTASSIUM DIHROMATE                             | A    | A              | A         |
| POTASSIUM FERROCYANIDE                          | A    |                | A         |
| POTASSIUM HYDROXIDE ( CAUSTIC POTASH )          | A    | C              | A         |
| POTASSIUM NITRATE                               | A    | A              | A         |
| POTASSIUM PERMANATE                             | A    |                | A         |
| POTASSIUM SALTS                                 | A    | A              |           |
| POTASSIUM SULFATE                               | A    | A              | A         |
| POTASSIUM SULFIDE                               | A    | A              | A         |
| POTASSIUM SULPHITE                              | A    | A              |           |
| PRESTONE ANTIFREEZE                             | A    | A              |           |
| PRL-HIGH TEMP. HYDR. OIL                        | D    | B              |           |
| PRODUCER GAS                                    | D    | B              |           |
| PROPANE ( LIQUIDIFIED )                         | D    | D              | A         |
| PROPANE PROPIONITRILE                           | D    | D              |           |
| PROPYL ACETATE                                  | B    | D              |           |
| PROPYL NITRATE                                  | B    | D              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                      | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|------------------------------------------------|------|----------------|-----------|
| P                                              |      |                |           |
| PROPYLENE                                      | D    | D              |           |
| PROPYLENE GLYCOL                               |      |                | A         |
| PROPYLENE OXIDE                                | B    | D              |           |
| P-S-661B                                       | D    | D              |           |
| PYDRAUL, 10E, 29ELT                            | B    |                |           |
| PYDRAUL, 115E                                  | B    | D              |           |
| PYDRAUL, 230E, 312C, 540C                      | D    | D              |           |
| PYDRAUL, 30E, 50E, 65E, 90E                    | B    | A              |           |
| PYRANOL                                        | D    | D              |           |
| PYRANOL, TRANSFORMER OIL                       | D    | D              |           |
| PYRIDINE                                       | B    | D              | A         |
| PYRIDINE OIL                                   | B    | D              |           |
| PYROGALLIC ACID                                |      |                | A         |
| PYROGARD 42, 43, 53, 55 (PHOSPHATE ESTER)      | A    | D              |           |
| PYROGARD, C, D                                 | D    | B              |           |
| PYROLIGNEOUS ACID                              | B    |                |           |
| PYROLUBE                                       | B    | B              |           |
| PYRROLE                                        | D    | B              |           |
| R                                              |      |                |           |
| RADIATION                                      | C    | C              |           |
| RAPESEED OIL                                   | A    | D              |           |
| RED LINE 100 OIL                               | D    | D              |           |
| RED OIL (MIL-H-5606)                           | D    | D              |           |
| R-J-1 (MIL-F-25558)                            | D    | D              |           |
| ROSINS                                         |      |                | A         |
| RP-1 (MIL-R-25576)                             | D    | D              |           |
| RUM                                            |      |                |           |
| RUST INHIBITORS                                |      |                |           |
| S                                              |      |                |           |
| SAL AMMONIAC                                   | A    | B              |           |
| SALAD DRESSINGS                                |      |                |           |
| SALICYLIC ACID                                 | A    |                |           |
| SALT WATER                                     | A    | A              |           |
| SANTO SAFE 300                                 | C    | A              |           |
| SEA WATER                                      | A    | A              | A         |
| SEWAGE                                         | B    | B              |           |
| SHELL ALVANIA GREASE #2                        | D    | B              |           |
| SHELL CARNEA 19 AND 29                         | D    |                |           |
| SHELL DIALA                                    | D    | D              |           |
| SHELL IRIS 3XF MINE FLUID (FIRE RESIST. HYDR.) | D    |                |           |
| SHELL IRIS 905                                 | D    | D              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                         | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-----------------------------------|------|----------------|-----------|
| S                                 |      |                |           |
| SHELL IRIS TELLUS #27, PET. BASE  | D    | D              |           |
| SHELL IRIS TELLUS #33             | D    | D              |           |
| SHELL IRIS UMF (5% AROMATIC)      | D    | D              |           |
| SHELL LO HYDRAX 27 AND 29         | D    | D              |           |
| SHELL MACOMA 72                   | D    | D              |           |
| SHELLAC ( BLEACHED )              |      |                | A         |
| SHELLAC ( ORANGE )                |      |                | A         |
| SILICATE ESTERS                   | D    | D              |           |
| SILICONE                          | A    | C              | A         |
| SILICONE GREASES                  | A    | C              |           |
| SILICONE OILS                     | A    | C              |           |
| SILVER BROMIDE                    |      |                | A         |
| SILVER NITRATE                    | A    | A              | A         |
| SINCLAIR, OPALINE CX-EPL LUBE     | D    | D              |           |
| SKELLY, SOLVENT B, C, E           | D    |                |           |
| SKYDROL 500                       | A    | C              |           |
| SKYDROL 7000                      | A    | C              |           |
| SOAP SOLUTIONS                    | A    | A              | A         |
| SOCONY MOBILE TYPE A              | D    | D              |           |
| SOCONY VACUUM AMV AC781 (GREASE)  | D    | D              |           |
| SOCONY VACUUM PD959B              | D    | D              |           |
| SODA ASH ( SEE SODIUM CARBONATE ) | A    | A              |           |
| SODIUM ACETATE                    | A    | D              | A         |
| SODIUM BICARBONATE                | A    | D              | A         |
| SODIUM BISULFATE                  | A    |                | A         |
| SODIUM BISULFITE                  | A    | A              | A         |
| SODIUM BORATE                     | A    | A              | A         |
| SODIUM CARBONATE                  | A    | A              | A         |
| SODIUM CHLORATE                   | A    |                | A         |
| SODIUM CHLORIDE                   | A    | A              | A         |
| SODIUM CHROMATE                   |      |                | A         |
| SODIUM CYANIDE                    | A    | A              | A         |
| SODIUM FLUORIDE                   | A    |                | A1        |
| SODIUM HYDROSULFITE               |      |                | A         |
| SODIUM HYDROXIDE                  | A    | B              |           |
| SODIUM HYDROXIDE ( 20% )          | A    | B              | A         |
| SODIUM HYDROXIDE ( 50% )          | A    | B              | A         |
| SODIUM HYDROXIDE ( 80% )          | A    | C              | A1        |
| SODIUM HYPOCHLORITE               | B    | B              |           |
| SODIUM HYPOCHLORITE ( < 20%)      | B    | B              | A         |
| SODIUM HYPOCHLORITE ( 100%)       | B    | B              | A         |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                          | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|------------------------------------|------|----------------|-----------|
| S                                  |      |                |           |
| SODIUM HYPOSULFATE                 |      |                | A         |
| SODIUM METAPHOSPHATE               | A    |                | A         |
| SODIUM METASILICATE                | A    |                | A         |
| SODIUM NITRATE                     | A    | D              | A         |
| SODIUM PERBORATE                   | A    | B              | A         |
| SODIUM PEROXIDE                    | A    | D              | A         |
| SODIUM PHOSPHATE (DIBASIC)         | A    | D              |           |
| SODIUM PHOSPHATE (MONO)            | A    | D              |           |
| SODIUM PHOSPHATE (TRIBASIC)        | A    | A              |           |
| SODIUM POLYPHOSPATE                | A    | D              | A         |
| SODIUM SALTS                       | A    | A              |           |
| SODIUM SILICATE                    | A    |                | A         |
| SODIUM SULFATE                     | A    | A              |           |
| SODIUM SULFIDE                     | A    | A              | A         |
| SODIUM SULFIDE                     | A    | A              |           |
| SODIUM SULFITE                     | A    | A              | A         |
| SODIUM TETRABORATE                 |      |                | A         |
| SODIUM THIOSULFATE ( HYPO )        | A    | A              | A         |
| SORGHUM                            |      |                |           |
| SOVASOL #1, 2 AND 3                | D    | D              |           |
| SOVASOL #73 AND 74                 | D    | D              |           |
| SOY SAUCE                          |      |                |           |
| SOYBEAN OIL                        | C    | A              |           |
| SPRY                               | B    | A              |           |
| SR-10 FUEL                         | D    | D              |           |
| SR-6 FUEL                          | D    | D              |           |
| STANDARD OIL MOBILUBE GX90-EP LUBE | D    | D              |           |
| STANNIC CHLORIDE                   | B    | B              |           |
| STANNIC CHLORIDE 50%               | B    | B              |           |
| STANNIC CHORIDE                    | B    | B              | A         |
| STANNIC FLUOBORATE                 |      |                |           |
| STANNOUS CHLORIDE                  | A    | B              | A         |
| STARCH                             | A    | D              | A         |
| STAUFFER 7700                      | D    | D              |           |
| STEAM, ABOVE 350°F                 | C    | D              |           |
| STEAM, BELOW 350°F                 | A    | D              |           |
| STEARIC ACID                       | B    | B              | A         |
| STODDARD SOLVENT                   | D    | D              | A         |
| STYRENE                            | D    | D              | A         |
| STYRENE (MONOMER)                  | D    | D              |           |
| SUCROSE SOLUTIONS                  | A    | A              |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|------------------------------------------|------|----------------|-----------|
| S                                        |      |                |           |
| SUGAR ( LIQUIDS )                        | A    | A              | A         |
| SULFATE ( LIQUORS )                      | A    |                | A         |
| SULFITE LIQUORS                          | B    | D              |           |
| SULFUR                                   | A    | A              |           |
| SULFUR CHLORIDE                          | D    | C              | A         |
| SULFUR DIOXIDE                           | A    | B              | A         |
| SULFUR DIOXIDE ( DRY )                   | A    | B              | A         |
| SULFUR DIOXIDE, LIQUIFIED UNDER PRESSURE | A    | B              |           |
| SULFUR DIOXIDE, WET                      | A    | B              |           |
| SULFUR HEXAFLUORIDE                      | A    | B              |           |
| SULFUR LIQUORS                           | B    | D              |           |
| SULFUR MOLTEN                            | C    | C              |           |
| SULFUR TRIOXIDE ( DRY )                  | B    | D              | A         |
| SULFURIC ACID ( < 10% )                  | B    | D              | A         |
| SULFURIC ACID ( 10-75% )                 | B    | D              | A         |
| SULFURIC ACID ( 75-100% )                | B    | D              | A         |
| SULFURIC ACID ( COLD CONC )              | B    | D              | A         |
| SULFURIC ACID ( HOT CONC )               | D    | D              | A         |
| SULFURIC ACID 20% OLEUM                  | D    | D              |           |
| SULFURIC ACID 3 MOLAR                    | B    | D              |           |
| SULFURIC ACID DILUTE                     | B    | D              |           |
| SULFUROUS ACID                           | B    | D              |           |
| SULFURYL CHLORIDE                        |      | D              | A         |
| SUNOCO #3661                             | D    | D              |           |
| SUNOCO ALL PURPOSE GREASE                | D    | D              |           |
| SUNOCO SAE10                             | D    | D              |           |
| SUNSAFE (FIRE RESIST.HYDR. FLUID)        | D    |                |           |
| SUPER SHELL GAS                          | D    | D              |           |
| SWAN FINCH EP LUBE                       | D    | D              |           |
| SWAN FINCH HYPOID-90                     | D    | D              |           |
| T                                        |      |                |           |
| TALLOW                                   |      |                | A         |
| TANNIC ACID                              | A    | B              | A         |
| TANNIC ACID 10%                          | A    | B              |           |
| TANNING LIQUORS                          | B    | B              | A         |
| TAR BITUMINOUS                           | D    | B              |           |
| TARTARRIC ACID                           | B    | A              | A         |
| TERPINEOL                                | C    |                |           |
| TERTABUTYL TITANATE                      | A    |                |           |
| TERTIARY BUTYL ALCOHOL                   | B    | B              |           |
| TERTIARY BUTYL CATECHOL                  | B    |                |           |

Chemicals / Chemikalien

- A - No effect / Keine Auswirkung  
B - Minor Effect-Good / Geringe Auswirkung  
C - Moderate Effect-Fair / Mäßige Auswirkung  
D - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
1 - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
2 - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                            | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|--------------------------------------|------|----------------|-----------|
| T                                    |      |                |           |
| TERTIARY BUTYL MERCAPTAN             | D    | D              |           |
| TETRABROMOMETHANE                    | D    | D              |           |
| TETRACHLOROETHANE                    |      | A              | A         |
| TETRACHLOROETHYLENE                  | D    |                | A         |
| TETRAETHYL LEAD                      | D    |                |           |
| TETRAETHYL LEAD "BLEND"              | D    |                |           |
| TETRAHYDROFURAN                      | B    |                | A         |
| TETRALIN                             | D    | D              |           |
| TEXACO 3450 GEAR OIL                 | D    | D              |           |
| TEXACO CAPELLA A AND AA              | D    | D              |           |
| TEXACO MEROPA #3                     | D    | D              |           |
| TEXACO REGAL B                       | D    | D              |           |
| TEXACO UNI-TEMP GREASE               | D    | B              |           |
| TEXAMATIC "A" TRANSMISSION OIL       | D    | D              |           |
| TEXAMATIC 1581 FLUID                 | D    | D              |           |
| TEXAMATIC 3525 FLUID                 | D    | D              |           |
| TEXAMATIC 3528 FLUID                 | D    | D              |           |
| TEXAMAYTIC 3401 FLUID                | D    | D              |           |
| TEXAS 1500 OIL                       | D    | B              |           |
| THIODOL TP-90B                       | A    |                |           |
| THIODOL TP-95                        | A    |                |           |
| THIONYL CHLORIDE                     | D    |                |           |
| TIDEWATER OIL MULTIGEAR 140, EP LUBE | D    | D              |           |
| TIDEWATER OIL-BEEDOL                 | D    | B              |           |
| TITANIUM TETRACHLORIDE               | D    | D              |           |
| TOLUENE ( TOLUOL )                   | D    | D              | A         |
| TOLUENE DIISOCYANIDS                 | B    | D              |           |
| TOMATO JUICE                         |      | D              | A         |
| TRANSFORMER OIL                      | D    | B              |           |
| TRANSMISSION FLUID TYPE A            | D    | B              |           |
| TRIACETIN                            | A    |                |           |
| TRIARYL PHOSPHATE                    | A    | C              |           |
| TRIBUTOXYETHYL PHOSPHATE             | A    |                |           |
| TRIBUTYL MERCAPTAN                   | D    | D              |           |
| TRIBUTYL PHOSPHATE                   | A    |                |           |
| TRICHLOROACETIC ACID                 | B    |                |           |
| TRICHLOROETHANE                      | D    | D              | A         |
| TRICHLOROETHYLENE                    | D    | D              | A         |
| TRICHLOROPROPANE                     |      | D              | A1        |
| TRICRESYLPHOSPATE                    | A    | C              | A         |
| TRIETHANOL AMINE                     | B    |                |           |

**Chemicals / Chemikalien**  
**A** - No effect / Keine Auswirkung  
**B** - Minor Effect-Good / Geringe Auswirkung  
**C** - Moderate Effect-Fair / Mäßige Auswirkung  
**D** - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
**1** - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
**2** - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                                       | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-------------------------------------------------|------|----------------|-----------|
| T                                               |      |                |           |
| TRIETHYL ALUMINUM                               |      |                |           |
| TRIETHYL BORANE                                 |      |                |           |
| TRIETHYLAMINE                                   |      | C              | A         |
| TRIFLUOROETHANE                                 | D    | D              |           |
| TRINITROTOLUENE                                 | D    |                |           |
| TRIOCTYL PHOSPHATE                              | A    | C              |           |
| TRIPOLY PHOSPHATE                               | A    | C              |           |
| TT-I-735B                                       | A    | A              |           |
| TT-N-95A                                        | D    | D              |           |
| TT-N-97B                                        | D    | D              |           |
| TT-S-735, TYPE I                                | D    | D              |           |
| TT-S-735, TYPE II                               | D    | D              |           |
| TT-S-735, TYPE III                              | D    | D              |           |
| TT-S-735, TYPE IV                               | D    | C              |           |
| TT-S-735, TYPE V                                | D    | C              |           |
| TT-S-735, TYPE VI                               | D    | C              |           |
| TT-T-656B                                       | A    | D              |           |
| TUNG OIL (CHINA WOOD OIL)                       | D    | D              |           |
| TURBINE OIL                                     | D    | D              |           |
| TURBINE OIL #15 (MIL-L-7808A)                   | D    | D              |           |
| TURBO OIL #35                                   | D    | D              |           |
| TURPENTINE                                      | D    | D              | A         |
| TYEP III FUEL (MIL-S-3136)                      | D    | D              |           |
| TYPE I FUEL (MIL-S-3136)                        | D    | D              |           |
| TYPE II FUEL (MIL-S-3136)                       | D    | D              |           |
| U                                               |      |                |           |
| UCON HYDROLUBE J-4                              | A    | A              |           |
| UCON LUBRICANT 50-HB100                         | A    | A              |           |
| UCON LUBRICANT 50-HB260                         | A    | A              |           |
| UCON LUBRICANT 50-HB5100                        | A    | A              |           |
| UCON LUBRICANT 50-HB55                          | A    | A              |           |
| UCON LUBRICANT 50-HB660                         | A    | A              |           |
| UCON LUBRICANT LB-1145                          | A    | A              |           |
| UCON LUBRICANT LB-135                           | A    | A              |           |
| UCON LUBRICANT LB-285                           | A    | A              |           |
| UCON LUBRICANT LB-300                           | A    | A              |           |
| UCON LUBRICANT LB-625                           | A    | A              |           |
| UCON LUBRICANT LB-65                            | A    | A              |           |
| UCON OIL 50-HB-280X (POLYACRYLON GLYCOL DERIV.) | A    | A              |           |
| UCON OIL LB-400X                                | A    | A              |           |
| UCON OIL LB-685                                 | A    | A              |           |

**Chemicals / Chemikalien**  
**A** - No effect / Keine Auswirkung  
**B** - Minor Effect-Good / Geringe Auswirkung  
**C** - Moderate Effect-Fair / Mäßige Auswirkung  
**D** - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
**1** - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
**2** - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                               | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-----------------------------------------|------|----------------|-----------|
| U                                       |      |                |           |
| UNIVIS 40 (HYDR. FLUID)                 | D    | D              |           |
| UNIVOLT #35 (MINERAL OIL)               | D    | D              |           |
| UNSYMMETRICAL DIMETHYL HYDRAZINE (UDMH) | A    | D              |           |
| URINE                                   | A1   | D              | A1        |
| V                                       |      |                |           |
| VARNISH                                 | D    | D              | A         |
| VEGETABLE JUICE                         |      | D              |           |
| VEGETABLE OIL                           | C    | A              |           |
| VINEGAR                                 | A    | A              | A         |
| VINYL CHLORIDE                          | B    |                |           |
| VRESILUBE                               | D    | C              |           |
| VV-B-680                                | A    | D              |           |
| VV-G-632                                | D    | C              |           |
| VV-G-671C                               | D    | C              |           |
| VV-H-910                                | A    | D              |           |
| VV-I-530A                               | D    | C              |           |
| VV-K-211D                               | D    | D              |           |
| VV-K-220A                               | D    | D              |           |
| VV-L-751B                               | D    | D              |           |
| VV-L-800                                | D    | C              |           |
| VV-L-820B                               | D    | C              |           |
| VV-L-825A, TYPE I                       | D    | C              |           |
| VV-L-825A, TYPE II                      | D    | C              |           |
| VV-O-526                                | D    | C              |           |
| VV-O-825A, TYPE III                     | D    | D              |           |
| VV-P-216A                               | D    | C              |           |
| VV-P-236                                | D    | D              |           |
| W                                       |      |                |           |
| WAGNER 21B BRAKE FLUID                  | A    | C              |           |
| WATER, ACID, MINE                       | A    | A              | A         |
| WATER, DISTILLED                        | A    | B              | A         |
| WATER, FRESH                            | A    | A              | A         |
| WATER, SALT                             | A    | B              | A         |
| WEMCO C                                 | D    | D              |           |
| WHEY                                    |      |                |           |
| WHISKEY AND WINES                       | A    | A              |           |
| WHITE OIL                               | D    | D              |           |
| WHITE PINE OIL                          | D    | D              |           |
| WOLMAR SALT                             | A    | A              |           |
| WOOD ALCOHOL                            | A    | A              |           |
| WOOD OIL                                | D    | D              |           |

**Chemicals / Chemikalien**  
**A** - No effect / Keine Auswirkung  
**B** - Minor Effect-Good / Geringe Auswirkung  
**C** - Moderate Effect-Fair / Mäßige Auswirkung  
**D** - Several Effect-Not recommended / unzulässige Auswirkungen - nicht empfohlen  
**1** - Satisfactory to 22°C (72°F) / Zufriedenstellend bis 22° (72F°)  
**2** - Satisfactory to 49°C (120°F) / Zufriedenstellend bis 22° (72F°)

| Chemicals                         | EPDM | MVQ 1<br>MVQ 2 | PTFE/ PFA |
|-----------------------------------|------|----------------|-----------|
| X                                 |      |                |           |
| XENON                             | A    | A              |           |
| XYLENE                            | D    | D              |           |
| XYLIDEPENES-MIXED-AROMATIC AMINES | D    | D              |           |
| XYLOL                             | D    | D              |           |
| Z                                 |      |                |           |
| ZEOLITES                          | A    |                |           |
| ZINC ACETATE                      | A    | D              |           |
| ZINC CHLORIDE                     | A    |                |           |
| ZINC SALTS                        | A    | A              |           |
| ZINC SULFATE                      | A    | A              |           |

Your local office

**Dockweiler AG**

An der Autobahn 10/20  
19306 Neustadt-Glewe  
Germany

Phone: + 49 38757 58-0  
Fax: + 49 38757 58-222  
E-mail: [sales@dockweiler.com](mailto:sales@dockweiler.com)  
Web: [www.dockweiler.com](http://www.dockweiler.com)